

Paramagnetic adsorbates on graphene: a charge transfer analysis

O. Leenaerts,^{*} B. Partoens,[†] and F. M. Peeters[‡]

Universiteit Antwerpen, Departement Fysica, Groenenborgerlaan 171, B-2020 Antwerpen, Belgium

(Dated: June 3, 2008)

We introduce a modified version of the Hirshfeld charge analysis method and demonstrate its accurateness by calculating the charge transfer between the paramagnetic molecule NO₂ and graphene. The charge transfer between paramagnetic molecules and a graphene layer as calculated with ab initio methods can crucially depend on the size of the supercell used in the calculation. This has important consequences for adsorption studies involving paramagnetic molecules such as NO₂ physisorbed on graphene or on carbon nanotubes.

PACS numbers: 68.43.-h, 73.20.Hb, 68.43.Bc, 81.05.Uw

The use of carbon nanotubes^{1,2,3,4,5,6} and more recently graphene⁷ as very sensitive gas sensors has stimulated a lot of theoretical work on this subject.^{8,9,10,11,12,13,14,15} Through ab initio calculations, one investigated the adsorption properties of these carbon materials and looked for the mechanisms behind their good sensing capabilities. It appears that the key issue is the charge transfer from the gas molecules to the carbon surface. Such ab initio calculations were able to provide good qualitative agreement with experiment, e.g. whether the gas molecules act as electron donors or acceptors, but a large variation in the size of the doping was found between different theoretical calculations. For example, the calculated charge transfer between a (10,0) single-walled carbon nanotube (SWNT) and a NO₂ molecule varies from⁹ $-0.015e$ to¹⁰ $-0.10e$, an order of magnitude difference! The size of the doping is, however, a crucial factor determining the sensitivity of the gas sensor. In this letter we demonstrate that important reasons for the discrepancies are: i) the different sizes of the supercells used in these ab initio calculations, and ii) the theoretical charge analysis method that has been used. We will show that the former is a very decisive parameter when the adsorbing molecules are paramagnetic. First we examine critically different theoretical charge analysis methods. Then we will perform ab initio calculations with different supercells to investigate the charge transfer dependence on the size of the supercell.

All our ab initio calculations were done within the density functional theory (DFT) formalism using the ABINIT¹⁶ software package within the local spin density approximation (LSD) and with Troullier-Martins pseudopotentials.¹⁷ We used a plane wave basis set with an energy cutoff of 816 eV, which was tested to give converged results for all the properties studied in this letter. Different graphene supercells ranging from 2×2 to 6×6 were implemented. For the sampling of the Brillouin zone (BZ) we used Monkhorst-Pack (MP) grids for the different supercells equivalent to a range from $12 \times 12 \times 1$ to $48 \times 48 \times 1$ points for a single unit cell.

To calculate the charge transfer from a molecule to a surface, one needs a physically meaningful and transparent approach to divide the electron density between them. A variety of methods has been developed for this

purpose, such as the Mulliken's¹⁸ or Bader's¹⁹ atoms in molecules approaches. We introduce a method based on the Hirshfeld²⁰ method and in particular the recently extended version of this approach, the Hirshfeld-I²¹ method. The simplicity and low cost of computation time makes the Hirshfeld method a very powerful approach in DFT calculations, and we will demonstrate that its extended version is more accurate than the Bader method and other Hirshfeld-based methods. In the Hirshfeld charge analysis, the total electron density ρ is divided between the different atoms of a system, according to the density of the neutral atoms, ρ_A^0 , in free space which build up this system: $Q_A = \int (\rho_A^0(\mathbf{r}) / \sum_{A'} \rho_{A'}^0(\mathbf{r})) \rho(\mathbf{r}) d\mathbf{r}$, with Q_A the charge on atom A (in units of e). The Hirshfeld-I method does not use the density of neutral atoms in free space, but uses the density of charged atoms instead. These charges on the different atoms are determined through an iterative process. One starts with the simple Hirshfeld method and determines the charge per atom. Then this charge is placed on the different atoms in free space and their densities are used to divide the density again among the atoms as with the simple Hirshfeld method. This procedure is repeated until the charges on the atoms are converged. In our approach we allow our system to relax completely and calculate the total density. Then we calculate the density of the molecule and the graphene layer separately in the same configuration as in the total relaxed system. These densities can now be used in the Hirshfeld-I method instead of the separate atomic densities. Such an approach gives charge transfers that are more physically meaningful as we will demonstrate in the following.

To test this charge analysis procedure we investigate the adsorption of the paramagnetic NO₂ molecule (with magnetic moment $M = 1\mu_B$) on a 4×4 graphene supercell. We calculate the charge transfer of the NO₂-graphene system using different theoretical approaches: we first use the simple Hirshfeld method, then we change the atomic densities into a molecular and a graphene density and use the same procedure; finally we put charges on NO₂ and graphene in order to use them in the Hirshfeld-I charge analysis. The Hirshfeld methods that use molecular densities instead of atomic densities will be referred to as the modified Hirshfeld and modified Hirshfeld-I

method. For comparison, we also calculated the charge transfer based on the Bader charge analysis. The charge transfer results are given in table I.

TABLE I: The charge transfer from graphene to NO₂ calculated with different methods.

method	charge transfer (e)
Hirshfeld	-0.099
modified Hirshfeld	-0.161
modified Hirshfeld-I	-0.181
Bader	-0.212
magnetic moment	-0.182

The advantage of using a paramagnetic molecule to demonstrate the accurateness of this charge transfer analysis method is that we can have a good estimate of the charge on the molecule through some physically relevant properties of the system, like the magnetic moment: extra charge in the partially occupied molecular orbital (POMO) of NO₂ will lower the magnetic moment of the NO₂ molecule. Extra charge on the graphene layer, on the other hand, will not effect its magnetic moment because pure graphene is diamagnetic²². This implies that we can simply use the lowering of the magnetic moment of the total system (i.e. the difference from $1\mu_B$) to estimate the charge transfer between the NO₂ molecule and graphene. This is very accurate if there is not too much hybridization between the molecular orbitals of NO₂ and the graphene orbitals. This is indeed the case for NO₂ since it physisorbs on graphene.^{13,14} The value of the charge transfer extracted from the lowering of the magnetic moment is $-0.182e$ (see table I), which is very close to the charge transfer obtained from the modified Hirshfeld-I method. The use of molecular densities instead of atomic ones leads already to a significant improvement of the simple Hirshfeld method and the iterative procedure makes the calculated charge transfer almost equal to the one extracted from the change in magnetic moment of the total system. The small difference of the order of $0.001e$ is caused by a small charge transfer due to orbital hybridization. This causes no change in the magnetic moment, but it is noticeable in the modified Hirshfeld-I charge analysis. Note also that the charge transfer from the Bader analysis does not correspond with the charge transfer from the lowering of the magnetic moment (see table I). Thus the modified Hirshfeld-I method gives a good approximation to the charge transfer in the adsorption process of paramagnetic molecules on graphene and, if the molecules are not paramagnetic, it is probably also more accurate to use this modified Hirshfeld-I charge analysis instead of e.g. the Bader charge analysis for a trustworthy determination of the charge transfer.

Another element of support for the modified Hirshfeld-I method is its geometrical interpretation. When we put an extra charge on a free standing paramagnetic molecule, it will be placed at the POMO. In the case of

a NO₂ molecule, this is an anti-bonding orbital which means that the bond length between the N and O atoms becomes larger when the POMO becomes filled. This fact can be used to estimate the charge transfer of a physisorbed NO₂ molecule to graphene by comparing the bond length of the relaxed physisorbed molecule with a charged free standing NO₂ molecule (see Fig. 1). From Fig. 1 we extract a charge transfer of $-0.206e$, which is close to the charge transfer obtained by the modified Hirshfeld-I method (and not close to the simple and modified Hirshfeld methods).

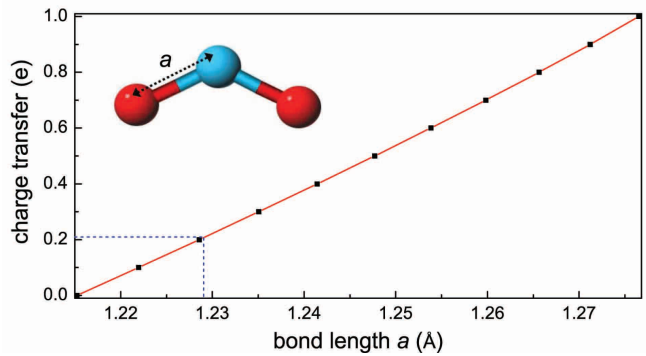


FIG. 1: (Color online) The dependence of the bond length of a NO₂ molecule on the extra charge put on the molecule.

Next we will discuss how the charge transfer for the case of paramagnetic molecules depends on the size of the supercell used in the ab initio calculations. The simulation of adsorption processes at surfaces is necessarily restricted to finite supercells. In most cases this gives a reasonably good approximation for e.g. charge transfer analyses in physisorption processes, but in some cases, when e.g. the adsorbates are paramagnetic, a different kind of charge transfer mechanism dominates the charge transfer^{13,14}, leading to very different results. We will use the NO₂ molecule again to show how sensitive the charge transfer can be with respect to the size of the used supercell. We make use of 4 different supercells, 2×2 , 3×3 , 4×4 , and 6×6 and several MP-grids for sampling the BZ. Fig. 2 shows that the charge transfers are converged reasonably well for a $24 \times 24 \times 1$ MP-grid.

There is a pronounced dependence of the charge transfer on the number of atoms in the simulated graphene layer²³ which can be explained by looking at the density of states (DOS) of the total system^{13,14} (see Fig. 3). The lowest unoccupied orbital (LUMO) of NO₂ is below the Dirac-point²⁴ of graphene, which causes a charge transfer to the molecule. This charge transfer depends clearly on the number of electronic states between the Dirac-point and the LUMO of the NO₂ molecule, which depends linearly on the number of carbon atoms in the supercell. Therefore, we may expect that if one takes a graphene supercell that is large enough, one would eventually get a charge transfer of one electron.¹³ However, it is clear from Fig. 2 that there is no simple linear depen-

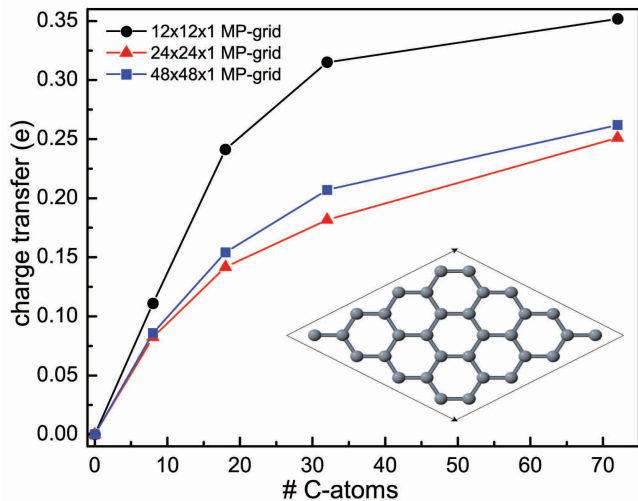


FIG. 2: (Color online) Supercell dependence of the charge transfer between a NO_2 molecule and graphene for different MP-grids. The inset shows a 4×4 graphene supercell.

dence. The position of the LUMO in the DOS depends on the filling of this orbital: the more electrons in the orbital the more difficult it gets to put another one in it and this translates in a shift of the LUMO towards the Dirac-point. In Fig. 4 we show this shift as a function of the number of carbon atoms in the supercell. It is not obvious that the orbital becomes totally filled (a transfer of one electron per paramagnetic molecule) before it coincides with the Dirac point, where the shift will stop and the charge transfer will be converged at a value of less than one electron per molecule.

Thus one can only obtain a quantitative meaningful value of the charge transfer between a paramagnetic molecule and a graphene layer in two cases: i) when the supercell used is large enough to get a charge transfer of one electron per molecule, or ii) the LUMO of the molecule coincides with the Dirac-point and the charge transfer has converged. In the case of the NO_2 molecule, one needs a supercell that is much larger than the 6×6 supercell we were able to use due to computational limitations. However, from Fig. 4 we find that if the LUMO stays partially full, it takes more than thousand carbon atoms to let it coincide with the Dirac-point. On the other hand, from Fig. 2 one may deduce that it is not unlikely that a charge transfer of $1e$ is reached before the supercell contains 1000 carbon atoms. From this we can conclude that probably the LUMO of NO_2 will be completely filled before it reaches the Dirac-point. This is compatible with the experimental observation⁷ that the charge transfer equals one electron charge per NO_2 molecule.

To conclude, we examined different methods to calculate the charge transfer between a paramagnetic molecule and a graphene layer and found that a modified Hirshfeld-

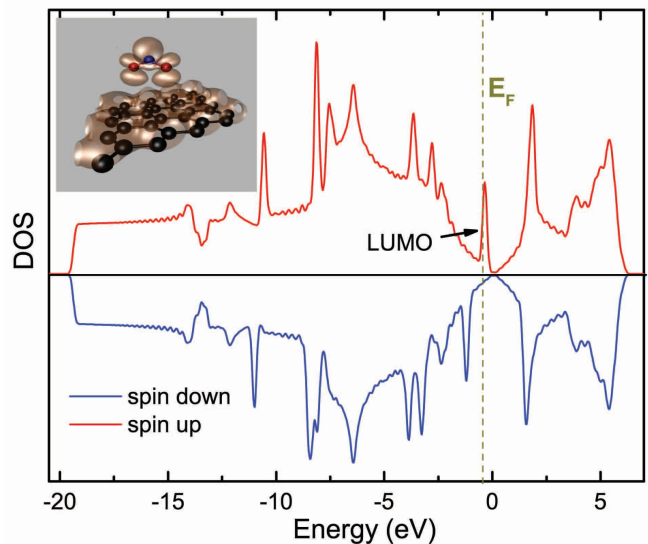


FIG. 3: (Color online) Spin-polarized DOS for NO_2 adsorbed on graphene calculated with a $60 \times 60 \times 1$ MP-grid for a 4×4 supercell. The LUMO of the NO_2 molecule and the Fermi-energy are indicated. The inset shows the orbitals of the NO_2 molecule (the LUMO) and graphene between which the electron transfer takes place.

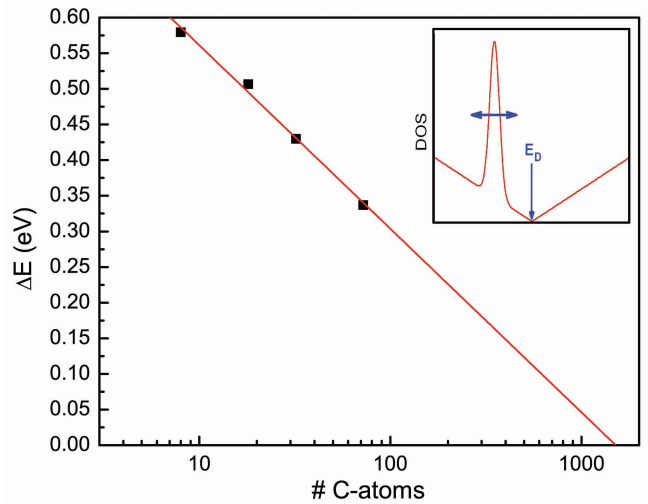


FIG. 4: (Color online) Distance, ΔE , of the NO_2 LUMO to the Dirac-point with respect to the number of carbon atoms used in the supercell. The inset shows a close-up of the total DOS of graphene with an adsorbed NO_2 molecule around the Dirac-point.

I method gives the most accurate and physically meaningful results. We used this method to investigate the dependence of the charge transfer on the size of the supercell in ab initio calculations and found that charge transfers involving paramagnetic molecules are, in a nontrivial way, very sensitive to the supercell size. We applied our results to the adsorption of NO_2 on graphene and showed that our ab initio calculations are compatible with the

experimentally found charge transfer of $1e$.⁷ In contrast to the claim in Ref. 13, we found that a charge transfer of $1e$ is not always realized for adsorption of a paramagnetic molecules on graphene. The present results are also valid for single wall carbon nanotubes because their adsorption properties are similar to those of graphene.¹⁴

Acknowledgments

This work was supported by the Flemish Science Foundation (FWO-VI), the NOI-BOF of the University of

Antwerp and the Belgian Science Policy (IAP). Discussions with C. Van Alsenoy are gratefully acknowledged.

-
- * Electronic address: ortwin.leenaerts@ua.ac.be
 - † Electronic address: bart.partoens@ua.ac.be
 - ‡ Electronic address: francois.peeters@ua.ac.be
 - ¹ J. Kong, N. R. Franklin, C. Zhou, M. G. Chapline, S. Peng, K. Cho, and H. Dai, *Science* **287**, 622 (2000).
 - ² J. Li, Y. Lu, Q. Ye, M. Cinke, J. Han, and M. Meyyappan, *Nano Letters* **3**, 929 (2003).
 - ³ K. Bradley, J.-C. P. Gabriel, M. Briman, A. Star, and G. Grüner, *Phys. Rev. Lett.* **91**, 218301 (2003).
 - ⁴ P. Qi, O. Vermesh, M. Grecu, A. Javey, Q. Wang, H. Dai, S. Peng, and K. J. Cho, *Nano Letters* **3**, 347 (2003).
 - ⁵ C. Staii, A. T. Johnson Jr., M. Chen, and A. Gelperin, *Nano Letters* **5**, 1774 (2005).
 - ⁶ X. Tang, S. Bansaruntip, N. Nakayama, E. Yenilmez, Y.-I. Chang, and Q. Wang, *Nano Letters* **6**, 1632 (2006).
 - ⁷ F. Schedin, A. K. Geim, S. V. Morozov, E. W. Hill, P. Blake, M. I. Katsnelson, and K. S. Novoselov, *Nature Materials* **6**, 652 (2007).
 - ⁸ S. Peng, and K. Cho, *Nanotechnology* **11**, 57 (2000).
 - ⁹ S. Santucci, S. Picozzi, F. Di Gregorio, L. Lozzi, C. Cantalini, L. Valentini, J. M. Kenny, and B. Delley, *J. Chem. Phys.* **119**, 10904 (2003).
 - ¹⁰ S. Peng, K. Cho, P. Qi, and H. Dai, *Chem. Phys. Lett.* **387**, 271 (2004).
 - ¹¹ J. Zhao, A. Buldum, J. Han, and J. P. Lu, *Nanotechnology* **13**, 195 (2002).
 - ¹² E. H. Hwang, S. Adam, and S. Das Sarma, *Phys. Rev. B* **76**, 195421 (2007).
 - ¹³ T. O. Wehling, K. S. Novoselov, S. V. Morozov, E. E. Vdovin, M. I. Katsnelson, A. K. Geim, and A. I. Lichtenstein, *Nano Letters* **8**, 173 (2008).
 - ¹⁴ O. Leenaerts, B. Partoens, and F. M. Peeters, *Phys. Rev. B* **77**, 125416 (2008).
 - ¹⁵ I. Zanella, S. Guerini, S. B. Fagan, J. M. Filho, and A. G. S. Filho, *Phys. Rev. B* **77**, 073404 (2008).
 - ¹⁶ URL: <http://www.abinit.org/>.
 - ¹⁷ N. Troullier, and J. L. Martins, *Phys. Rev. B* **43**, 1993 (1991).
 - ¹⁸ R. S. Mulliken, *J. Chem. Phys.* **23**, 2343 (1955).
 - ¹⁹ R. F. Bader, *Chem. Rev.* **91**, 893 (1991).
 - ²⁰ F. L. Hirshfeld, *Theor. Chim. Acta* **44**, 129 (1977).
 - ²¹ P. Bultinck, C. Van Alsenoy, P. W. Ayers, and R. Carbó-Dorca, *J. Chem. Phys.* **126**, 144111 (2007).
 - ²² J. W. McClure, *Phys. Rev.* **104**, 666 (1956).
 - ²³ The number of atoms in the simulated graphene layer is equal to twice the number of unit cells in the supercell.

²⁴ The Dirac-point is the Fermi-level of pure graphene.